



Cite this: *Dalton Trans.*, 2015, **44**, 8833

Nanoheterogeneous catalysis in electrochemically induced olefin perfluoroalkylation†

Yulia B. Dudkina,*^a Tatyana V. Gryaznova,^a Yuri N. Osin,^b Vadim V. Salnikov,^b Nikolay A. Davydov,^a Svetlana V. Fedorenko,^a Asia R. Mustafina,^a David A. Vivic,^c Oleg G. Sinyashin^a and Yulia H. Budnikova^a

Ni-catalyzed electroreductive olefin perfluoroalkylation affords both monomeric and dimeric products depending on the reaction media. Recycling of the catalyst can be achieved by immobilization of a (bpy)-NiBr₂ complex on silica nanoparticles decorated with anchoring amino-groups. Switching the homogeneous and heterogeneous catalysts is found to be one more factor to control the product ratio. This catalytic technique is both green and atom economical and combines the advantages of nanoheterogeneous catalysis and electrocatalysis.

Received 20th January 2015,
Accepted 30th March 2015

DOI: 10.1039/c5dt00269a

www.rsc.org/dalton

Introduction

Nowadays green and sustainable development of chemical processes requires advanced transformations and pollution abatement. Some of the more sophisticated chemical transformations involve homogeneous catalysis. In a number of instances, however, industrial application of homogeneous catalysis is complicated by difficulties in separating catalysts and products. These problems are particularly significant in the case of noble and/or toxic organometallic species.¹ Converting homogeneous catalysis into heterogeneous catalysis is one approach for facilitating separations and making such transformations more environmentally friendly. Heterogenation of known catalytically active transition metal complexes, such as those based on nickel and palladium, is an attractive strategy for modern day coupling reactions, due to easy separation and recycling of the catalyst.

Traditional micrometric scale catalysts widely used in the chemical industry show lower activity and selectivity in comparison with homogeneous catalysts owing to steric and diffusion factors.^{2,3} As the size of the system decreases to nanoscale the surface area of the support increases, reactions

may suffer from the formation of homogeneous bulk emulsions.^{3,4} Another advantage of the use of nanoparticles is that they are not porous supports and they do not exhibit difficulties in reagents and products transport to/from catalytic centres and bulk solution.

Nanocomposites have been tested in some catalytic and classical organic reactions,^{1,5} cross-couplings, and photocatalysis,⁶ but have never been used in electrochemical reactions. The closest electrochemical examples are systems based on polymer matrices containing organic moieties capable of coordination to transition metal ions. Such systems are obtained by electrochemical anode dissolution in the presence of a polymeric ligand, although the catalytic transformation step occurs without electrochemical aid.⁷

In recent years, electrochemically generated catalysts have become increasingly important both for fine organic synthesis and for detailed studies of electron transfer, bond cleavage/breaking, substitution, addition and other reactions. One area that may benefit from the development of heterogeneous electrochemical methods is organofluorine chemistry. Organofluorine compounds are widely used in biochemistry, medical, and materials chemistry due to their unique properties.⁸ Among the fluorine-containing functional groups, perfluoroalkyl groups are of special interest and new methods for their incorporation into organic substrates are needed.⁹

Recently, we developed a one-step electrocatalytic homogeneous fluoroalkylation of olefinic substrates promoted by reduced Ni complexes bearing α -diimine ligands, which led to dimeric addition-dimerization products.¹⁰ A way to prevent the dimerization process and to obtain a monomeric product is also shown in these studies.^{10e}

The present study combines the advantages of two different approaches—nanoheterogeneous catalysis (easy catalyst recy-

^aA.E. Arbuzov Institute of Organic and Physical Chemistry, Kazan Scientific Center, Russian Academy of Sciences, 8 Arbuzov str., Kazan 420088, Russian Federation. E-mail: dudkinayu@iopc.ru

^bKazan Federal University, Interdisciplinary Center of Analytical Microscopy, 18 Kremlevskaya St., Kazan 420018, Russian Federation

^cDepartment of Chemistry, Lehigh University, 6 East Packer Avenue, Bethlehem, Pennsylvania 18015, USA

† Electronic supplementary information (ESI) available: Text, figures giving ¹H, ¹³C, and ¹⁹F NMR spectra. CCDC 1038179 (R/S) and 1038180 (SS/RR). For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c5dt00269a

cling) and electrocatalysis (generation and regeneration of the catalyst active form on the electrode surface without any additional molecular reductant)—to develop a new effective catalytic technique that is both green and atom economical. Such a technique offers exceptional control over the phase behavior and catalyst separation.

Results and discussion

The overall goal of this work is to develop a nanoheterogeneous catalyst for olefin fluoroalkylations (Table 1) and to find ways to control the product ratio (monomer/dimer) in the reactions. Moreover, it is important to compare the activity and selectivity of the heterogeneous process with the previously studied homogeneous ones for future reaction development. The reaction described in Table 1 was investigated. Previously tested α -methylstyrene¹⁰ and α ,4-dimethylstyrene were used as the organic substrates, $\text{H}(\text{CF}_2)_6\text{I}$ was used as the perfluoroalkyl source due to its convenience for ^1H NMR analysis, and the $[(\text{bpy})\text{NiBr}_2]$ complex was used as the catalyst as it was previously found to be very effective for similar electrocatalytic reactions.¹⁰ Switching homogeneous and heterogeneous catalysts is accompanied with changes under several reaction conditions. The role of the reactant stoichiometries, the amount and the state of the catalyst (homogeneous or immobilized), and the presence of water (carried by silica nanoparticles synthesized in an aqueous solution) were considered in optimizations.

The joint electrochemical reduction of olefin and perfluoroalkyl halide (1:1) in anhydrous DMF at the potential of $[(\text{bpy})\text{NiBr}_2]$ reduction (-1.5 V) was shown to afford a domi-

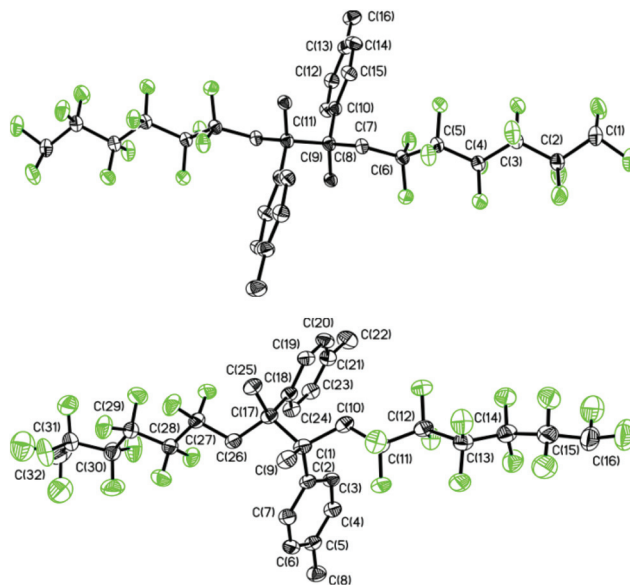


Fig. 1 ORTEP diagrams of **1a**: *R,S* (top) and *S,S/R,R* (bottom) isomers. All H atoms are omitted for clarity.

nant addition–dimerization product.¹⁰ Thereafter the joint electro-reduction of α ,4-dimethylstyrene and 6-*H*-perfluoro-hexyl iodide in the presence of $[(\text{bpy})\text{NiBr}_2]$ (10 mol%) gave the dimeric product **1a** in 71% yield (entry 1). Two isolated stereoisomers of **1a** were separated from the reaction mixture and are characterized crystallographically† (Fig. 1). Decreasing the catalyst amount to 1 mol% resulted in lowering of the yield by 10% (entry 2).

Switching the reaction media to a DMF–water mixture afforded both dimeric and monomeric products in dimethylstyrene perfluoroalkylation (Table 1, entry 3). Although the general yield was lower in comparison with anhydrous DMF media, the result presented water as a more convenient, available and environmentally friendly alternative to $\text{Bu}_3\text{SnH}^{10e}$ as the hydrogen atom source in the monomeric product synthesis.

Conversion of a homogeneous catalyst to a heterogeneous one results from immobilization of the Ni(II) complex on silica

Table 1 Perfluoroalkylation of α ,4-dimethylstyrene^a

Entry	Solvent	Catalyst	1a/1b	Total yield [%]
1	DMF	$(\text{bpy})\text{NiBr}_2$ (10%)	1.0 : 0.0 ^b	71
2	DMF	$(\text{bpy})\text{NiBr}_2$ (1%)	1.0 : 0.0 ^b	60
3	DMF– H_2O (4 : 1)	$(\text{bpy})\text{NiBr}_2$ (1%)	1.0 : 0.8	48
4	DMF– H_2O (4 : 1)	$(\text{bpy})\text{NiBr}_2$ (1%) on AEPTS-SNs	1.0 : 0.45	44

^a Reaction conditions: substrate ratio 1 : 1, $Q = 2F$ per $\text{H}(\text{CF}_2)_6\text{I}$, -1.5 V.

^b Monomeric product was observed in trace amounts.

† Crystal data for **1a** *R/S* isomer: formula $\text{C}_{32}\text{H}_{26}\text{F}_{24}$, $M_w = 866.53$, $a = 7.7287(9)$, $b = 24.374(3)$, $c = 9.3149(11)$ Å, $\beta = 102.310(3)^\circ$, $V = 1714.4(3)$ Å³, $\rho_{\text{calc.}} = 1.679$ g cm⁻³, $\mu = 0.189$ mm⁻¹, empirical absorption correction ($0.956 \leq T \leq 0.970$), $Z = 2$, monoclinic, space group $P2_1/n$, $T = 135$ K, ω scans, 27 008 reflections collected ($\pm h, \pm k, \pm l$), $\theta_{\text{max}} = 27.90^\circ$, 4084 independent ($R_{\text{int}} = 0.031$) and 3237 observed reflections [$I \geq 2\sigma(I)$], 254 refined parameters, $R = 0.054$, $wR^2 = 0.140$, max. residual electron density 0.58 (-0.31) e Å⁻³, hydrogen atoms calculated and refined as riding atoms.

Crystal data for **1a** *SS/RR* isomer: formula $\text{C}_{32}\text{H}_{26}\text{F}_{24}$, $M_w = 866.53$, $a = 27.503(2)$, $b = 11.0537(9)$, $c = 11.5143(9)$ Å, $\beta = 99.686(2)^\circ$, $V = 3450.5(5)$ Å³, $\rho_{\text{calc.}} = 1.668$ g cm⁻³, $\mu = 0.188$ mm⁻¹, empirical absorption correction ($0.956 \leq T \leq 0.993$), $Z = 4$, monoclinic, space group $P2_1/c$, $T = 135$ K, ω scans, 55 864 reflections collected ($\pm h, \pm k, \pm l$), $\theta_{\text{max}} = 27.84^\circ$, 8158 independent ($R_{\text{int}} = 0.054$) and 4583 observed reflections [$I \geq 2\sigma(I)$], 519 refined parameters, $R = 0.074$, $wR^2 = 0.200$, max. residual electron density 0.42 (-0.40) e Å⁻³, hydrogen atoms calculated and refined as riding atoms.

nanoparticles (SNs). The immobilization may be distinguished by physical and/or electrostatic adsorption of metal complexes at the silica/water interface or by inner sphere coordination of Ni(II) complexes *via* some anchoring groups at the silica surface. The [(bpy)NiBr₂] complex lacks a net positive charge, but in theory it can be fixed at the silica surface through coordination bonds with convenient anchoring groups such as amino-groups.

The SNs were obtained as 35 ± 5 nm sized beads¹¹ through a well-documented water-in-oil microemulsion procedure¹² and decorated by treatment with 3-[2-(2-aminoethylamino)-ethylamino]propyltrimethoxysilane (AEPTS).¹³ The fluorescamine-based quantitative fluorescence analysis¹⁴ revealed the average number of NH₂ groups to be 3500 per SN. Immobilization of the [(bpy)NiBr₂] complex on the SNs was performed by mixing their aqueous solutions, followed by phase separation of the SNs with further washing of the separated SNs with DMF in order to remove water (see the ESI† for details). The average number of the Ni(II) complex (3700) per SN was calculated from the difference between the concentrations of the Ni(II) complex in the aqueous solution before and after the immobilization on the SNs. This number is in good agreement with the number of NH₂ groups per SN, which suggests coordination bonds *versus* physical or electrostatic adsorption as the main driving force of the immobilization. Fig. 2 shows schematic representation of the AEPTS-SNs. The average size of the SNs with the immobilized catalyst was 55 ± 5 nm. The SEM (scanning electron microscopy) images of the AEPTS-SNs with the immobilized [(bpy)NiBr₂] complex before and after fluoroalkylation reaction are shown in Fig. 3.

Comparison of homogeneous and heterogeneous reactions performed under the same conditions (DMF–water ratio, amount of the catalyst) shows a difference in the monomer–dimer ratio, however the total yields do not depend on the catalyst phase (Table 1, entries 3 and 4). The amount of the monomeric product was lower in reactions with the immobilized catalyst. The ratio of the dimer's diastereomeric forms (*S/R* and *RR/SS* isomers) did not depend on the catalyst phase and the reaction media. According to NMR spectra (¹H

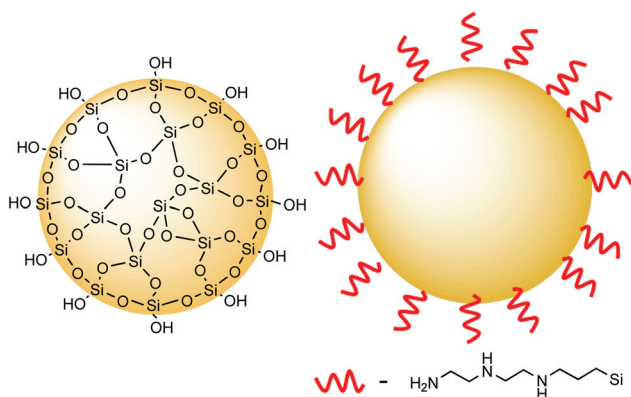


Fig. 2 Schematic representation of the AEPTS-SNs.

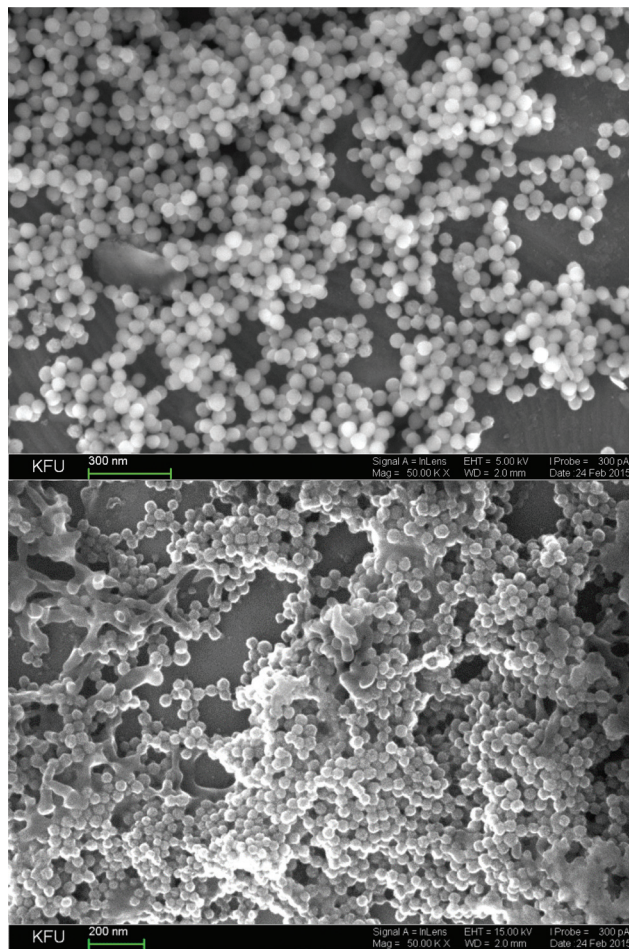



Fig. 3 SEM (scanning electron microscopy) images of the AEPTS-SNs with an immobilized [(bpy)NiBr₂] complex before (top) and after fluoroalkylation reaction (bottom).

and ¹⁹F) it was equal to 1 : 1 in reactions with α -methylstyrene and $\alpha,4$ -dimethylstyrene. The amount of electricity passed was found to have no effect on the monomer–dimer ratio. The total yield did not increase by passing over 2F electricity per perfluoroalkyl halide.

A set of experiments with varied catalysts and organic solvent–water ratios were carried out to determine the parameters affecting the product ratio in α -methylstyrene perfluoroalkylation (Table 2).

Water was found to promote the monomeric product formation that is illustrated in Table 2 by entries 1 and 2 with 89 and 80% DMF and entries 3 and 4 with 80 and 67% DMF respectively, while no transformation of the olefinic substrate was observed in pure water media (entry 5). The optimal DMF–water ratio affording both products in good yields was found to be 4 : 1.

A monomeric product was obtained in a reaction with the immobilized catalyst performed in dry DMF (Table 2, entry 6), however, in lower yields than that seen in entries 1 and 2 (DMF–water mixtures) of Table 2. Reaction 3 carried out with

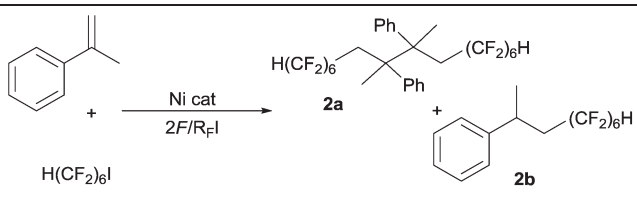Table 2 Perfluoroalkylation of α -methylstyrene^a


Entry	Solvent	Catalyst	2a/2b	Total yield [%]
1	DMF–H ₂ O (8 : 1)	(bpy)NiBr ₂ (1%) on AEPTS-SNs	1.0 : 1.7	48
2	DMF–H ₂ O (4 : 1)	(bpy)NiBr ₂ (1%) on AEPTS-SNs	1.0 : 1.4	45
3	DMF–H ₂ O (4 : 1)	(bpy)NiBr ₂ (1%) + added AEPTS-SNs	1.0 : 2.7	46
4	DMF–H ₂ O (2 : 1)	(bpy)NiBr ₂ (1%) + added AEPTS-SNs	1.0 : 4.1	29
5	H ₂ O	(bpy)NiBr ₂ (10%)	No reaction	
6	DMF	(bpy)NiBr ₂ (1%) on AEPTS-SNs	1.0 : 0.8	53
7	DMF–H ₂ O (4 : 1)	(bpy)NiBr ₂ (1%)	1.0 : 3.8	44
8	DMF–H ₂ O (4 : 1)	(bpy)NiBr ₂ (1%), BuNH ₂ ^b	1.0 : 3.5	48
9	CH ₃ CN–H ₂ O (4 : 1)	(bpy)NiBr ₂ (1%) on AEPTS-SNs	1.0 : 1.1	41
10 ^c	DMF–H ₂ O (4 : 1)	(bpy)NiBr ₂ (10%)	1.0 : 1.1	94

^a Reaction conditions: substrate ratio 1 : 1, $Q = 2F$ per H(CF₂)₆I, –1.5 V.

^b Substrates : catalyst : BuNH₂ ratio is 1 : 1 : 0.01 : 0.1. ^c α -Methylstyrene : H(CF₂)₆I ratio is 1 : 4.

the homogeneous catalyst and admixture of AEPTS-SNs shows the average monomer–dimer ratio between the homogeneous catalysis (entry 7) and heterogeneous catalysis (entry 2) under the same conditions. Thus the dimerization reactions are preferred when the catalyst is immobilized at the heterogeneous silica surface. Presumably, less access to water molecules near the hydrophobic AEPTS-SN surface containing immobilized and metal-containing active sites suppresses the rate of monomer formation. A model synthesis (entry 8) in dry DMF with addition of BuNH₂ revealed no influence of the surface amino groups on the reaction. Replacement of DMF with acetonitrile in aqueous organic media did not affect the yields and the product ratio for reactions with the immobilized catalyst (entry 9).

The data presented in Tables 1 and 2 reveal that the immobilization of [(bpy)NiBr₂] on the AEPTS-SNs is one more factor affecting the monomer–dimer ratio in electrocatalytic perfluoroalkylation reactions. This tendency suggests an impact of coordination bonds *versus* physical and/or electrostatic adsorption in the immobilization of the [(bpy)NiBr₂] complex on the AEPTS-SNs. Immobilization of the [(bpy)NiBr₂] complex through outer-sphere coordination with aminoethyl-aminoethylaminopropyl groups at the SN surface is suggested to hinder access of water to the coordination site which can be the reason for the aforementioned different monomer : dimer ratios. The post-catalysis picture (Fig. 3, bottom) shows no signs of the catalyst reduction to metal nanoparticles. The


catalytic reaction occurs at nickel centers, so the catalyst active form is not metal nanoparticles, but low-valent nickel species immobilized on the modified surface of silica nanoparticles.

The decrease in total yields of the isolated products in reactions carried out in aqueous organic media is likely associated with partial deactivation of the catalyst active forms by water. Such reactivity is known for nickel-catalysed electroreductive reactions in proton-donor media.¹⁵

Higher product yields can be achieved by increasing the amount of perfluoroalkyl halide. Thus, joint electrolysis of α -methylstyrene, 6-*H*-perfluorohexyl iodide (1 : 4 ratio), [(bpy)NiBr₂] (10 mol%) led to a mixture of dimeric and monomeric products in a 1.0 : 1.1 ratio in 94% total yield (entry 10, Table 2).

Another challenging aim of the study was to estimate the stability of the immobilized catalyst and its capability for recycling. No leakage of the Ni(II) complex immobilized on the AEPTS-SNs was detected by electrochemical analysis (the lower detection limit is 10^{–4} M) of the washing DMF solutions. The washing solutions were obtained through the phase separation of the DMF and aqueous-DMF dispersions of the AEPTS-SNs (10.9 g L^{–1}) with the immobilized [(bpy)NiBr₂] complex (1.7 × 10^{–3} M). The elemental analysis revealed that the amount of nickel on the support (Ni : Si ratio) did not decrease after reaction, which also confirms that there is no leakage of the catalyst into the bulk solution. Moreover the Ni : Br ratio after reaction was found to be 1 : 2, which shows that the bromide likely remains coordinated to nickel during the catalytic cycle. Moreover, a catalytic test of the filtrate showed that it is not catalytically active, no transformation of the olefinic substrate was observed (see the ESI†). Thus, there is no leaching of the complex from the support.

The immobilized catalyst was tested in several reaction cycles in α -methylstyrene perfluoroalkylation. The results in Table 3 demonstrate that the yields of the product from reactions run with a recycled catalyst do not vary, supporting a heterogeneous reaction process. After each round shown in

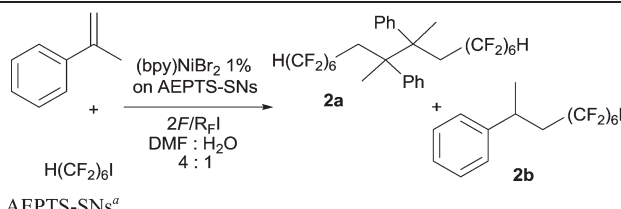Table 3 Use of the recycled (bpy)NiBr₂ catalyst (1%) immobilized on AEPTS-SNs^a


Number of repeats	2a/2b	Total yield [%]
1	1.0 : 1.4	45
2	1.0 : 1.1	42
3	1.0 : 0.8	42

^a Reaction conditions: substrates ratio 1 : 1, $Q = 2F$ per H(CF₂)₆I, –1.5 V.

Table 3, the reaction mixture was centrifuged to separate the immobilized catalyst. The nanoparticles were washed with a DMF–water mixture (4 : 1), dispersed in water and used directly for the next synthesis. Triple use of such a catalyst led only to a negligible decrease in the product yield. After three reaction cycles no loss of the catalytic activity of the immobilized catalyst was observed.

Conclusions

The present work employs inner-sphere coordination of [(bpy)NiBr₂] through amino-groups fixed on the surface of the amino-decorated silica nanoparticles as an efficient tool to switch from homogeneous to heterogeneous perfluoroalkylation catalysis. The introduced heterogeneous catalyst preparation provides sustained immobilization of the complex on AEPTS-SNs. The absence of leaching was confirmed by several independent techniques. After easy and quantitative separation from the reaction mixture the catalyst retains its high catalytic activity and can be reused. The results indicate that the addition of water to the reaction mixture increases the monomer/dimer ratio significantly.

Although the diffusion coefficient was supposed to be an important factor for the system efficiency as the catalyst active form regeneration occurs at the electrode surface, we found it to be negligible. No difference in electrosynthesis proceeding with homogeneous and heterogeneous catalysts was observed, and the electrosynthesis parameters (the cell current and potential) were the same for galvanostatic (cathodic current density from 2 to 50 mA cm⁻²) and potentiostatic processes at the cathode potential equal to the first reduction wave for [(bpy)NiBr₂] (–1.5 V vs. Ag/AgNO₃ reference electrode).

It should be mentioned that the electrocatalytic reactions reported herein generate sites of potential chirality, and we are currently exploring possibilities of enantioselective olefin perfluoroalkylations catalyzed by nickel complexes containing chiral ligands such as pybox (pybox = 2,6-bis[(4S)-4-phenyl-2-oxazolonyl]pyridine).

Acknowledgements

This work was supported by a RFBR grant 14-03-31774. D.A.V. thanks the Office of Basic Energy Sciences of the U.S. Department of Energy (DE-FG02-07ER15885).

Notes and references

- (a) P. D. Stevens, G. Li, J. Fan, M. Yen and Y. Gao, *Chem. Commun.*, 2005, 4435; (b) S. Ko and J. Jang, *Angew. Chem.*, 2006, **118**, 7726. S. Ko and J. Jang, *Angew. Chem., Int. Ed.*, 2006, **45**, 7564.
- H. F. Rase, *Handbook of commercial catalysts: Heterogeneous catalysts*, CRC Press, New York, 2000.
- T. J. Yoon, W. Lee, Y.-S. Oh and J.-K. Lee, *New J. Chem.*, 2003, **27**, 227.
- (a) Y. H. Zhu, C. N. Lee, R. A. Kemp, N. S. Hosmane and J. A. Maguire, *Chem. – Asian J.*, 2008, **3**, 650–662; (b) D. Astruc, F. Lu and J. R. Aranzas, *Angew. Chem.*, 2005, **117**, 8062–8083. D. Astruc, F. Lu and J. R. Aranzas, *Angew. Chem., Int. Ed.*, 2005, **44**, 7852–7872.
- (a) R. F. Heck, *Org. React.*, 1982, **27**, 345; (b) J. E. Plevyak and R. F. Heck, *J. Org. Chem.*, 1978, **43**, 2454; (c) R. F. Heck, *Acc. Chem. Res.*, 1979, **12**, 146; (d) W. Cabri and I. Candiani, *Acc. Chem. Res.*, 1995, **28**, 2; (e) I. P. Beletskaya and A. V. Cheprakov, *Chem. Rev.*, 2000, **100**, 3009; (f) M. T. Reetz and E. Westermann, *Angew. Chem.*, 2000, **112**, 170; M. T. Reetz and E. Westermann, *Angew. Chem., Int. Ed.*, 2000, **39**, 165; (g) A. Biffis, M. Zecca and M. Basato, *J. Mol. Catal. A: Chem.*, 2001, **173**, 249; (h) Z. Wang, P. Xiao, B. Shen and N. He, *Colloids Surf., A*, 2006, **276**, 116.
- S. Rawalekar and T. Mokari, *Adv. Energy Mater.*, 2013, **3**, 12.
- (a) T. V. Magdesieva, O. M. Nikitin, E. V. Zolotukhina, V. A. Zinovieva and M. A. Vorotyntsev, *Mendeleev Commun.*, 2012, **22**, 305; (b) T. V. Magdesieva, O. M. Nikitin, O. A. Levitsky, V. A. Zinovieva, I. Bezverkhy, E. V. Zolotukhina and M. A. Vorotyntsev, *J. Mol. Catal. A: Chem.*, 2012, **50**, 353–354; (c) T. V. Magdesieva, O. M. Nikitin, O. V. Polyakova, A. V. Yakimansky, M. Y. Goikhman and I. V. Podeshvo, *ECS Trans.*, 2011, **35**, 1; (d) T. V. Magdesieva, O. M. Nikitin, S. M. Masoud, A. V. Yakimansky, M. Y. Goikhman and I. V. Podeshvo, *Russ. Chem. Bull.*, 2011, **60**, 1601; (e) T. V. Magdesieva, O. M. Nikitin, A. V. Yakimansky, M. Y. Goikhman and I. V. Podeshvo, *Electrochim. Acta*, 2011, **56**, 3666.
- (a) J.-P. Bégué and D. Bonnet-Delpon, *Bioorganic and Medicinal Chemistry of Fluorine*, John Wiley & Sons, Inc., Hoboken, NJ, 2008; (b) P. Kirsch, *Modern Fluoroorganic Chemistry*, Wiley-VCH, Weinheim, 2nd edn, 2013; (c) S. Purser, P. R. Moore, S. Swallow and V. Gouverneur, *Chem. Soc. Rev.*, 2008, **37**, 320; (d) *Fluorine in Medicinal Chemistry and Chemical Biology*, ed. I. Ojima, John Wiley & Sons, 2009.
- (a) J.-A. Ma and D. Cahard, *Chem. Rev.*, 2004, **104**, 6119; (b) O. A. Tomashenko and V. V. Grushin, *Chem. Rev.*, 2011, **111**, 4475.
- (a) D. Y. Mikhaylov, Y. H. Budnikova, T. V. Gryaznova, D. V. Krivolapov, I. A. Litvinov, D. A. Vicic and O. G. Sinyashin, *J. Organomet. Chem.*, 2009, **694**, 3840; (b) D. Y. Mikhaylov, T. V. Gryaznova, Y. G. Budnikova and O. G. Sinyashin, *Russ. Chem. Bull., Int. Ed.*, 2010, **59**, 1918; (c) D. Y. Mikhaylov, Y. H. Budnikova, T. V. Gryaznova and O. G. Sinyashin, *ECS Trans.*, 2009, **25**, 67; (d) M. N. Khrizanforov, T. V. Gryaznova, D. Y. Mikhailov, Y. H. Budnikova and O. G. Sinyashin, *Russ. Chem. Bull., Int. Ed.*, 2012, **61**, 1560; (e) D. Mikhaylov, T. Gryaznova, Y. Dudkina, M. Khrizanphorov, S. Latypov, O. Kataeva, D. A. Vicic, Y. Budnikova and O. G. Sinyashin, *Dalton Trans.*, 2012, **41**, 165; (f) Y. B. Dudkina, D. Y. Mikhailov, T. V. Gryaznova, S. G. Fattakhov, Y. G. Budnikova and

- O. G. Sinyashin, *Russ. Chem. Bull., Int. Ed.*, 2013, **62**, 2362; (g) D. Y. Mikhaylov and Y. H. Budnikova, *Russ. Chem. Rev.*, 2013, **82**, 835; (h) Y. B. Dudkina, M. N. Khrizanforov, T. V. Gryaznova and Y. H. Budnikova, *J. Organomet. Chem.*, 2014, **751**, 301.
- 11 A. R. Mustafina, S. V. Fedorenko, O. D. Konovalova, A. Y. Menshikova, N. N. Shevchenko, S. E. Soloveva, A. I. Konovalov and I. S. Antipin, *Langmuir*, 2009, **25**, 3146.
- 12 (a) F. J. Arriagada and K. Osseo-Asare, *J. Colloid Interface Sci.*, 1999, **211**, 210; (b) R. P. Bagwe, C. Yang, L. R. Hilliard and W. H. Tan, *Langmuir*, 2004, **20**, 8336.
- 13 (a) R. P. Bagwe, L. R. Hilliard and W. Tan, *Langmuir*, 2006, **22**, 4357; (b) N. Davydov, A. Mustafina, V. Burilov, E. Zvereva, S. Katsyuba, L. Vagapova, A. Konovalov and I. Antipin, *ChemPhysChem*, 2012, **13**, 3357.
- 14 H. Ritter and D. Brühwiler, *J. Phys. Chem.*, 2009, **113**, 10667.
- 15 V. Courtois, R. Barhadi, S. Condon and M. Troupel, *Tetrahedron Lett.*, 1999, **40**, 5993.